



Test Report

Report No. TC.26.02.000814-R₁

Date of Issue 2026-03-10



Applicant: hokon GmbH & Co KG

Applicant Address: Wasserbank 21, Witten, Germany

Sample Description: Melamine Faced Bamboo Chipboard

Style No.: 062A-18mm

Manufacturer: Foshan King Fad New Material Technology Co., Ltd.

End Use: Furniture; Decoration

Receipt Date of Sample: Received on 2026-02-13

Date of Testing: From 2026-02-13 to 2026-03-06

Sample Submitted: The Sample(s) and Its (Their) Information(s) Was (Were) Submitted by Applicant and Identified.

Test Result: Refer to Next Page.

TÜV SÜD SW Rail Transportation Technology (Jiangsu) Co., Ltd.

Prepared by:

Noah

Noah Zhong

Approved by:

Leo Wang

Leo Wang

Note:

(1) Each order is subject to acceptance of our [General Terms and Conditions](#) and the [TÜV SÜD Testing, Certification, Validation and Verification Regulation](#), in the version valid at the time the contract is concluded. For full version of above both documents, please visit the link to view.

(2) The results in this report are relevant only to the sample(s) tested.

(3) The test report shall not be reproduced except in full without the written approval of the laboratory.

(4) Disclaimer Measurement Uncertainty:

Unless otherwise stated, the decision rule for conformity reporting is based on Binary Statement for Simple Acceptance Rule (w=0) stated in ILAC-G8:09/2019 or CNAS-GL015:2022.

Regd. Office:
TÜV SÜD SW Rail Transportation
Technology (Jiangsu) Co., Ltd.
Test location: Changzhou

Phone: +86/0519-81239872
Fax: +86/0519-81239872-123
E-mail: czx.qm@tuvsud.com
Web: <http://www.tuvsud.com>


Address:
Building 17, Innovative Industry Park, No. 377
Wuyinan Road, National High and New Technology &
Industry Development Zone, Wujin, 213015 P.R. China

Test Report

Report No. TC.26.02.000814-R₁

Date of Issue 2026-03-10

Description of the test subject

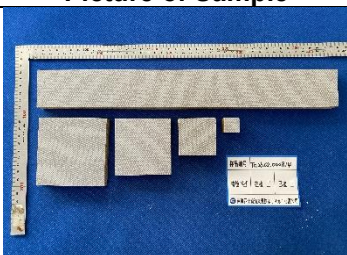Sample	Description	Picture of Sample
001	Melamine Faced Bamboo Chipboard	
		

Conclusion:

Test Items	Standard	Conclusion
1 Bending properties	DIN EN 310:1993	Pass
2 Density	DIN EN 323:1993	Pass
3 Moisture content	DIN EN 322:1993	Pass
4 Tensile strength perpendicular to the plane of the board	DIN EN 319:1993	Pass
5 Surface soundness	DIN EN 311:2002	Pass
6 Swelling in thickness after immersion in water	DIN EN 317:1993	Pass
7 Resistance to axial withdrawal of screws	DIN EN 320:2011	Pass
8 Formaldehyde Emission test	EN 717-1:2004	Pass
9 REACH SVHC_253 Content Test	Regulation (EC) No 1907/2006 (REACH Act)	Pass

Note: This Report is to Supersede Test Report No. TC.26.02.000814 Issued on 2026-03-09.



Test Report

Report No. TC.26.02.000814-R₁

Date of Issue 2026-03-10

Test Results

1. Bending properties

Test method: DIN EN 310:1993

Sample conditioning: (20±2)°C,(65±5)%RH,264h

Test environment: 21.8°C,48%RH

Test equipment: Universal material testing machine MC-JB-053, Digital calipers MC-JB-300,

Digital outside micrometer MC-JB-303

Diameter of loading edge: 30mm

Diameter of supports: 15mm

Span: 364mm

Test speed: 10mm/min

Horizontal:

Sample No.	Test surface	Bending strength (N/mm ²)	Modulus of elasticity in bending (N/mm ²)
1	Top	21.8	4.77×10 ³
2		24.0	4.19×10 ³
3		23.6	4.41×10 ³
4	Bottom	26.2	4.50×10 ³
5		26.9	4.30×10 ³
6		22.3	4.37×10 ³
Average	-	24.1	4.42×10 ³
Client's requirement	-	≥11.0	≥1600
Conclusion	-	Pass	Pass

Longitudinal:


Sample No.	Test surface	Bending strength (N/mm ²)	Modulus of elasticity in bending (N/mm ²)
1	Top	17.7	3.50×10 ³
2		18.1	3.45×10 ³
3		19.6	3.54×10 ³
4	Bottom	19.7	3.45×10 ³
5		21.3	3.38×10 ³
6		18.3	3.45×10 ³
Average	-	19.1	3.46×10 ³
Client's requirement	-	≥11.0	≥1600
Conclusion	-	Pass	Pass

Test Report

Report No. TC.26.02.000814-R₁

Date of Issue 2026-03-10

Test photos:

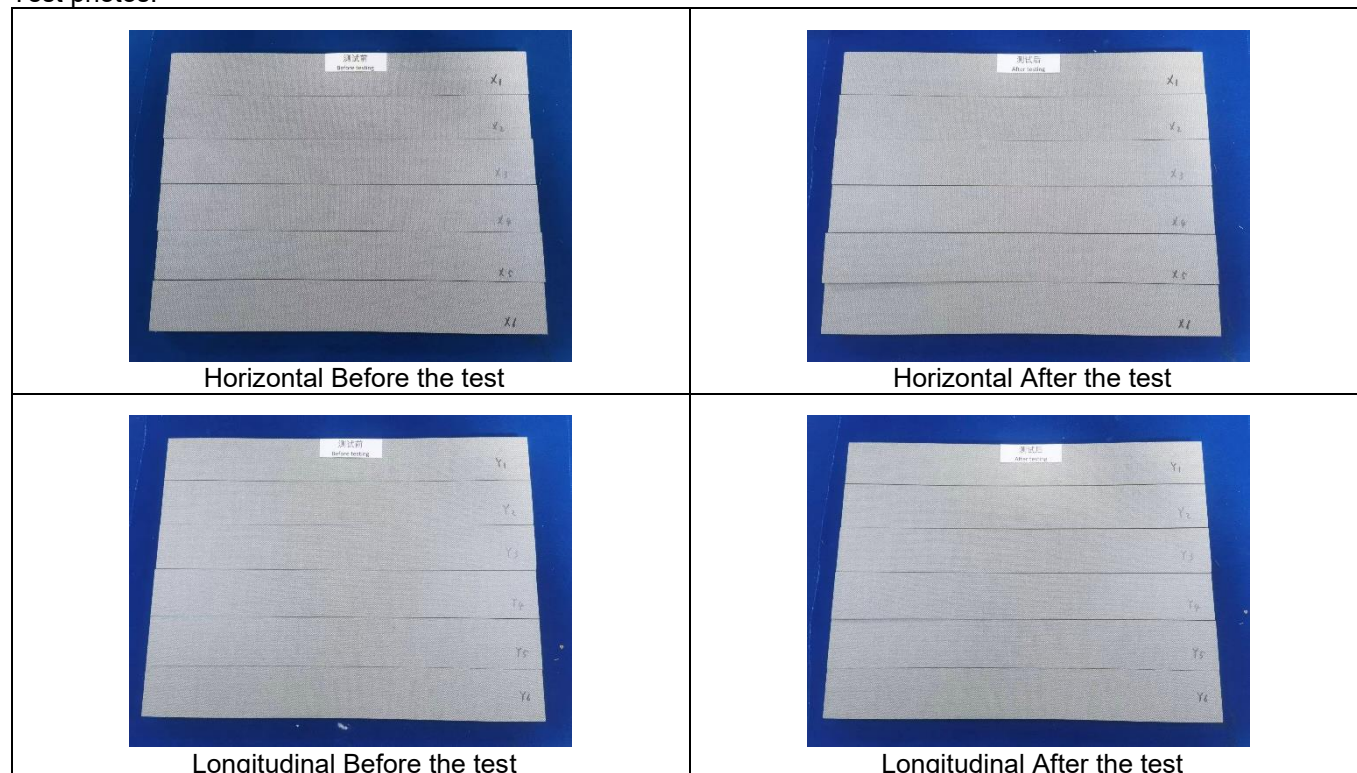

Test Report

Report No. TC.26.02.000814-R₁

Date of Issue 2026-03-10

2. Density

Test method: DIN EN 323:1993

Sample conditioning: (20±2)°C, (65±5)%RH, 264h

Test equipment: 21.5°C, 52%RH

Test equipment: Electronic balance MC-JB-016, Digital indicator MC-JB-300,

Digital outside micrometer MC-JB-303

Sample No.	Density (kg/m ³)	Average (kg/m ³)	Client's requirement (kg/m ³)	Conclusion
1	714.517	712.162	550-750	Pass
2	711.554			
3	710.853			
4	710.973			
5	710.360			
6	714.715			

3. Moisture content

Test method: DIN EN 322:1993


Test environment: 22.8°C, 54%RH

Test equipment: Electronic balance MC-JB-016, High temperature test chamber MC-JB-002

Test temperature: (103±2)°C

Sample No.	Moisture content (%)	Average (%)	Client's requirement (%)	Conclusion
1	4.4	4.5	4.5-13	Pass
2	4.7			
3	4.4			
4	4.4			

Test photos:

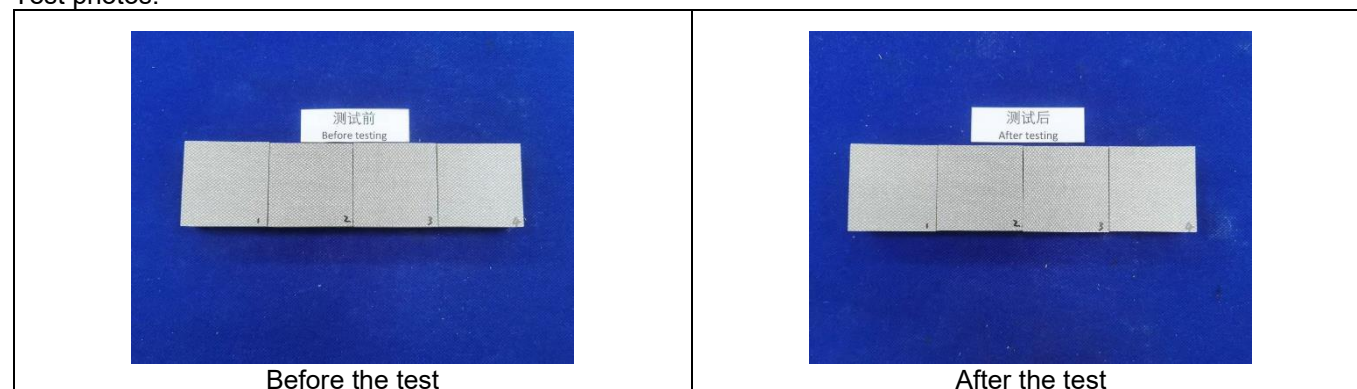

Test Report

Report No. TC.26.02.000814-R₁

Date of Issue 2026-03-10

4. Tensile strength perpendicular to the plane of the board

Test method: DIN EN 319:1993

Sample conditioning: (20±2)°C, (65±5)%RH, 264h

Test environment: 21.8°C, 50%RH

Test equipment: Universal material testing machine MC-JB-053, Digital calipers MC-JB-300

Test speed: 1mm/min

Sample No.	Tensile strength perpendicular to the plane of the board (N/mm ²)	Average (N/mm ²)	Client's requirement (N/mm ²)	Conclusion
1	0.79	0.93	≥0.35	Pass
2	0.94			
3	0.54			
4	0.95			
5	1.12			
6	1.16			
7	0.77			
8	1.16			

Test photos:



Test Report

Report No. TC.26.02.000814-R₁

Date of Issue 2026-03-10

5. Surface soundness

Test method: DIN EN 311:2002

Sample conditioning: (20±2)°C, (65±5)%RH, 264h

Test environment: 22.3°C, 50%RH


Test equipment: Electronic Universal Tester MC-JB-010, Digital calipers MC-JB-300

Surface area: 1000mm²

Test speed: 2mm/min

Sample No.	Failure mode	Surface soundness (N/mm ²)	Average (N/mm ²)	Client's requirement (N/mm ²)	Conclusion
1	80% within underlying board+20% between adhesive and board	1.95	2.20	≥0.8	Pass
2	80% within underlying board+20% between adhesive and board	1.90			
3	80% within underlying board+20% between adhesive and board	2.35			
4	100% within underlying board	2.32			
5	100% within underlying board	2.39			
6	100% within underlying board	1.88			
7	80% within underlying board+20% between adhesive and board	2.32			
8	100% within underlying board	2.52			


Test photos:

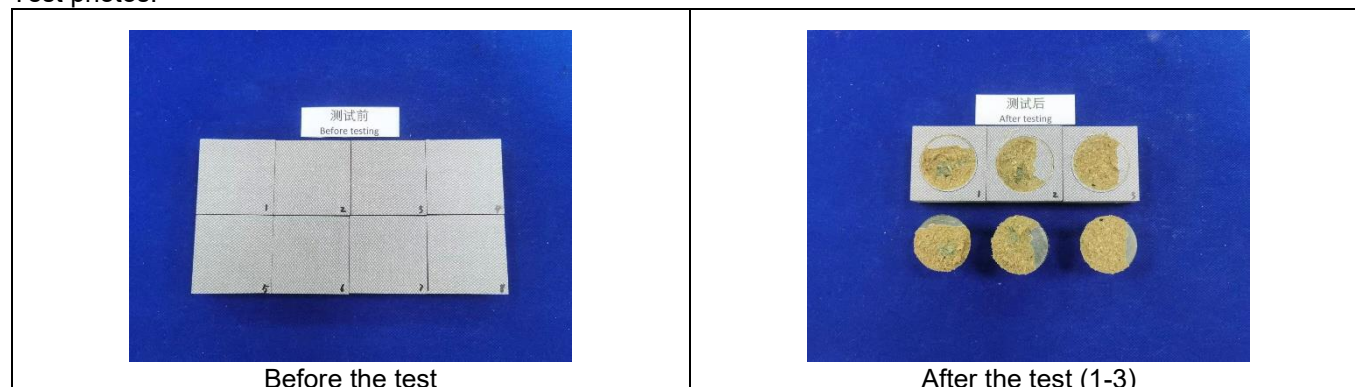

Test Report

Report No. TC.26.02.000814-R₁

Date of Issue 2026-03-10

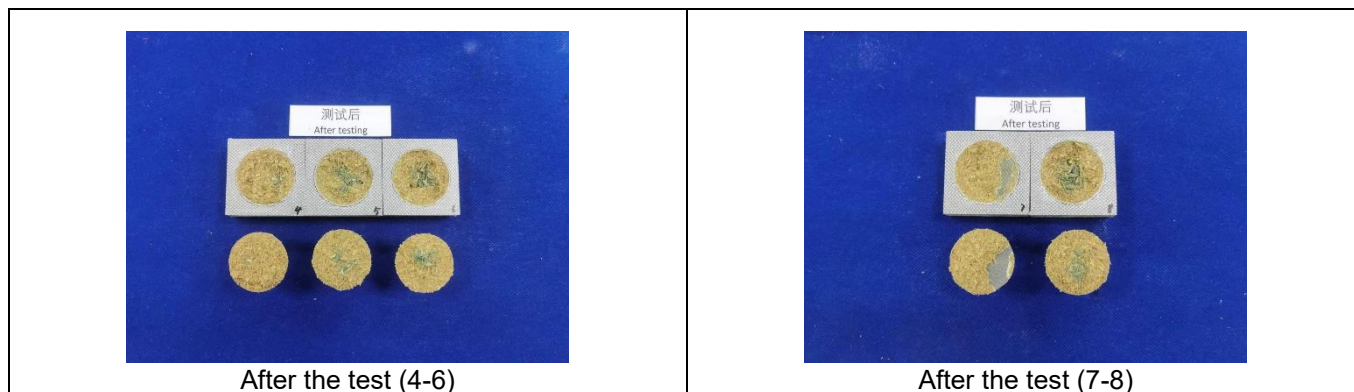

Test Report

Report No. TC.26.02.000814-R₁

Date of Issue 2026-03-10

6. Swelling in thickness after immersion in water

Test method: DIN EN 317:1993

Sample conditioning: (20±2)°C, (65±5)%RH, 264h


Test environment: 22.3°C, 51%RH

Test equipment: Constant temperature water bath MC-JB-026, Digital outside micrometer MC-JB-303

Test time: 24h

Sample No.	Swelling in thickness after immersion in water (%)	Average (%)	Client's requirement (%)	Conclusion
1	0.8	0.8	≤14	Pass
2	0.7			
3	0.8			
4	0.8			
5	0.9			
6	0.8			
7	0.8			
8	0.9			

Test photos:

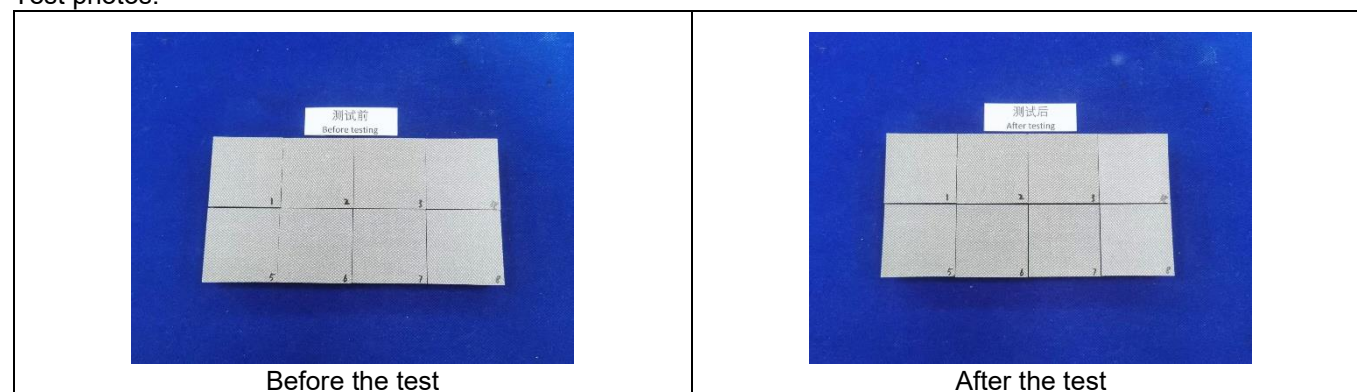

Test Report

Report No. TC.26.02.000814-R₁

Date of Issue 2026-03-10

7. Resistance to axial withdrawal of screws

Test method: DIN EN 320:2011

Sample conditioning: (20±2)°C, (65±5)%RH, 264h


Test environment: 22.3°C, 50%RH

Test equipment: Electronic Universal Tester MC-JB-010, Digital calipers MC-JB-300

Test speed: 10mm/min

Sample No.	The face screwholding (N)	The edge screwholding (N)
1	1550	1240
2	1330	1240
3	1350	1430
Average	1410	1300
Client's requirement	≥1000	≥800
Conclusion	Pass	Pass

Test photos:

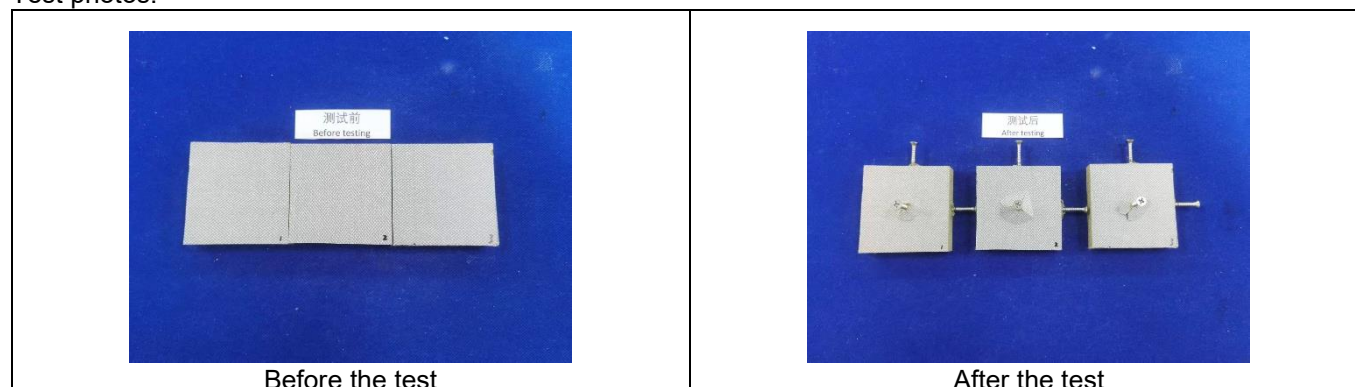



Test Report

Report No. TC.26.02.000814-R₁

Date of Issue 2026-03-10

8. Formaldehyde Emission test

Test method: EN 717-1:2004, analysed by UV-VIS

Test condition:

Chamber volume: 1m³

Relative humidity: (45.0±3.0)%

Temperature: (23±0.5)°C

Air exchange rate: 1.0/h

Air velocity: (0.1~0.3)m/s

Loading factor: (1.0±0.02)m²/m³

Item	Unit	Method Detection Limit	Result	Client's requirement
Formaldehyde emission	mg/m ³	0.01	N.D.	≤0.124

Remark: N.D. = Not detected, less than Method Detection Limit

9. REACH SVHC 253 Content Test

Analysis of the 253 substances of very high concern (SVHC) on the Candidate List for authorization, concerning Regulation (EC) No. 1907/2006 as published on the European Chemicals Agency (ECHA) website.

Test Method: Analysis based on LCMS, GCMS, Headspace-GCMS, ICP-OES/AAS, UV-VIS and XRF.

Parameters	Result (%)	Requirement (%)
253 substances of very high concern	N.D.	0.1

Remark 1 1) Notification: In accordance with Regulation (EC) No. 1907/2006, any producer or importer of articles shall notify ECHA, in accordance with paragraph 4 of Article 7, if a substance meets the criteria in Article 57 and is identified in accordance with Article 59(1), if both the following conditions are met:
(a) the substance is present in those articles in quantities totalling over 1 tonne per producer or importer per year;
(b) the substance is present in those articles above a concentration of 0,1 % weight by weight (w/w).
2) Communication:
In accordance of Article 33 of Regulation (EC) No. 1907/2006 (REACH regulation), any supplier of an article containing a substance meeting the criteria in Article 57 and identified in accordance with Article 59(1) in concentration above 0.1% weight by weight (w/w) shall provide the recipient of the article with sufficient information, available to the supplier, to allow safe use of the article including, as a minimum, the name of that substance. On request by a consumer the relevant information shall be provided by any supplier of an article free of charge, within 45 days of receipt of the request.

Remark 2: Method Detection Limit=0.010%
N.D. = Not detected, less than MDL.
Appendix I for Each Substance List



Test Report

Report No. TC.26.02.000814-R₁

Date of Issue 2026-03-10

Remark 3: ** The substances are tested in terms of its respective elements and the test result is based on the calculation of selected elements/ market(s) and to the worst-case scenario. Due to the limit of the analytical technology available, any further investigation is not feasible. The client is strongly advised to review the chemical formulation to ascertain.
 ## The substances are UVCB(substance of unknown or variable composition, complex reaction products or biological materials), which are identified by its main constituents. Individual concentrations to the constituent of UVCB with an amount of <0.01% were not considered by the calculation of the sum. Calculation is based on the worst-case scenario. Due to the UVCB nature the reported values may be regarded as semi-quantitative.
 # only applicable with ≥0.1% of Michler's ketone(CAS No. 90-94-8) or Michler's base (CAS No. 101-61-1)
 TGIC is a mixture and also contains β-TGIC. According to ECHA's technical dossier the ratio of β-TGIC to TGIC is around 1 to 10. Therefore β-TGIC is issued based on the above-mentioned ratio.

Appendix I

No.	Substance Name	CAS No
1.	Benzyl butyl phthalate (BBP)	85-68-7
2.	Bis (2-ethylhexyl) phthalate (DEHP)	117-81-7
3.	Dibutyl phthalate (DBP)	84-74-2
4.	4,4'-Diaminodiphenylmethane (MDA)	101-77-9
5.	5-tert-butyl-2,4,6-trinitro-m-xylene (musk xylene)	81-15-2
6.	Alkanes, C10-13, chloro (Short Chain Chlorinated Paraffins)	85535-84-8
7.	Cobalt Dichloride**	7646-79-9
8.	Hexabromocyclododecane (HBCDD)	25637-99-4/ 3194-55-6
9.	Sodium dichromate, dihydrate**	7789-12-0/ 10588-01-9
10.	Anthracene	120-12-7
11.	Lead hydrogen arsenate**	7784-40-9
12.	Bis(tributyltin)oxide (TBTO)	56-35-9
13.	Diarsenic pentaoxide**	1303-28-2
14.	Diarsenic trioxide**	1327-53-3
15.	Triethyl arsenate**	15606-95-8
16.	2,4-Dinitrotoluene	121-14-2
17.	Anthracene oil##	90640-80-5
18.	Anthracene oil, anthracene paste, distn, lights##	91995-17-4
19.	Anthracene oil, anthracene paste, anthracene fraction##	91995-15-2
20.	Anthracene oil, anthracene-low##	90640-82-7
21.	Anthracene oil, anthracene paste##	90640-81-6
22.	Lead chromate**	7758-97-6
23.	Lead chromate molybdate sulphate red (C.I. Pigment Red 104)**	12656-85-8
24.	Lead sulfochromate yellow (C.I. Pigment Yellow 34)**	1344-37-2
25.	Diisobutyl phthalate (DIBP)	84-69-5
26.	Tris(2-chloroethyl)phosphate	115-96-8
27.	Pitch, coal tar, high temperature##	65996-93-2
28.	Acrylamide	79-06-1
29.	Trichloroethylene	79-01-6



Test Report

Report No. TC.26.02.000814-R₁

Date of Issue 2026-03-10

Appendix I

No.	Substance Name	CAS No
30.	Boric acid**	10043-35-3/ 11113-50-1
31.	Disodium tetraborate, anhydrous**	1330-43-4/ 12179-04-3
32.	Tetraboron disodium heptaoxide, hydrate(calculate as decahydrate)**	12267-73-1
33.	Sodium chromate**	7775-11-3
34.	Potassium chromate**	7789-00-6
35.	Ammonium dichromate**	7789-09-5
36.	Potassium dichromate**	7778-50-9
37.	Cobalt(II) sulphate**	10124-43-3
38.	Cobalt(II) dinitrate**	10141-05-6
39.	Cobalt(II) carbonate**	513-79-1
40.	Cobalt(II) diacetate **	71-48-7
41.	2-Methoxyethanol	109-86-4
42.	2-Ethoxyethanol	110-80-5
43.	Chromium trioxide**	1333-82-0
44.	Acids generated from chromium trioxide and their oligomers: a. Chromic acid** b. Dichromic acid ** c. Oligomers of chromic acid and dichromic acid **	7738-94-5/ 13530-68-2 --
45.	2-Ethoxyethyl acetate (2-EEA)	111-15-9
46.	Strontium chromate**	7789-06-2
47.	1,2-Benzenedicarboxylic acid, di-C7-11-branched and linear alkyl esters (DHNUP)	68515-42-4
48.	Hydrazine	7803-57-8 302-01-2
49.	1-Methyl-2-pyrrolidone	872-50-4
50.	1,2,3-Trichloropropane	96-18-4
51.	1,2-Benzenedicarboxylic acid, di-C6-8-branched alkyl esters, C7-rich (DIHP)	71888-89-6
52.	1,2-Dichloroethane	107-06-2
53.	2,2'-Dichloro-4,4'-methylenedianiline (MOCA)	101-14-4
54.	2-Methoxyaniline, o-Anisidine	90-04-0
55.	4-tert-Octylphenol	140-66-9
56.	Aluminosilicate Refractory Ceramic Fibres**	--
57.	Arsenic acid **	7778-39-4
58.	Bis(2-methoxyethyl) ether	111-96-6
59.	Bis(2-methoxyethyl) phthalate	117-82-8
60.	Calcium arsenate**	7778-44-1
61.	Dichromium tris(chromate) **	24613-89-6
62.	Formaldehyde, oligomeric reaction products with aniline (technical MDA)	25214-70-4
63.	Lead diazide**	13424-46-9
64.	Lead dipicrate**	6477-64-1
65.	Lead styphnate **	15245-44-0
66.	N,N-dimethylacetamide (DMAC)	127-19-5
67.	Pentazinc chromate octahydroxide**	49663-84-5



Test Report

Report No. TC.26.02.000814-R₁

Date of Issue 2026-03-10

Appendix I

No.	Substance Name	CAS No
68.	Phenolphthalein	77-09-8
69.	Potassium hydroxyoctaoxodizincatedichromate**	11103-86-9
70.	Trilead diarsenate**	3687-31-8
71.	Zirconia Aluminosilicate, Refractory Ceramic Fibres**	--
72.	1,2-bis(2-methoxyethoxy)ethane (TEGDME; triglyme)	112-49-2
73.	1,2-dimethoxyethane;ethylene glycol dimethyl ether (EGDME)	110-71-4
74.	4,4'-bis(dimethylamino)-4''-(methylamino)trityl alcohol [#]	561-41-1
75.	4,4'-bis(dimethylamino)benzophenone (Michler's ketone)	90-94-8
76.	4-[4,4'-bis(dimethylamino)benzhydrylidene] cyclohexa-2,5-dien-1-ylidene]dimethylammo- nium chloride(C.I. Basic Violet 3) [#]	548-62-9
77.	[4-[[4-anilino-1-naphthyl][4-(dimethylamino) phenyl]methylene]cyclohexa-2,5-dien-1-ylidene]dimethylammonium chloride (C.I. Basic Blue 26) [#]	2580-56-5
78.	Diboron trioxide**	1303-86-2
79.	Lead(II)bis(methanesulfonate)**	17570-76-2
80.	Formamide	75-12-7
81.	N,N,N',N'-tetramethyl-4,4'-methylenedianiline (Michler's base)	101-61-1
82.	TGIC(1,3,5-tris(oxiranylmethyl)-1,3,5-triazine-2,4,6(1H,3H,5H)-trione)	2451-62-9
83.	α,α-Bis[4-(dimethylamino)phenyl]-4 (phenylamino)naphthalene-1-methanol (C.I. Solvent Blue 4) [#]	6786-83-0
84.	β-TGIC(1,3,5-tris[(2S and2R)-2,3-epoxypropyl] 1,3,5-triazine-2,4,6-(1H,3H,5H)-trione)	59653-74-6
85.	Bis(pentabromophenyl) ether (DecaBDE)	1163-19-5
86.	Pentacosafuorotridecanoic acid	72629-94-8
87.	Tricosafuorododecanoic acid	307-55-1
88.	Henicosafuoroundecanoic acid	2058-94-8
89.	Heptacosafuorotetradecanoic acid	376-06-7
90.	4-(1,1,3,3-tetramethylbutyl)phenol, ethoxylated-covering well-defined substances and UVCB substances, polymers and homologue (OPEO)	--
91.	4-Nonylphenol, branched and linear -substances with a linear and/or branched alkyl chain with a carbon number of 9 covalently bound in position 4 to phenol, covering also UVCB- and well-defined substances which include any of the individual isomers or a combination thereof (NP)	--
92.	Diazene-1,2-dicarboxamide (C,C'-azodi(formamide))	123-77-3
93.	Cyclohexane-1,2-dicarboxylic anhydride (Hexahydrophthalic anhydride - HHPA)	85-42-7
94.	Hexahydromethylphthalic anhydride, Hexahydro-4-methylphthalic anhydride, Hexahydro-1-methylphthalic anhydride, Hexahydro-3-methylphthalic anhydride	25550-51-0 19438-60-9 48122-14-1 57110-29-9
95.	Methoxy acetic acid	625-45-6
96.	1,2-Benzenedicarboxylic acid, dipentylester, branched and linear	84777-06-0
97.	Diisopentylphthalate (DIPP)	605-50-5
98.	N-pentyl-isopentylphtalate	--
99.	1,2-Diethoxyethane	629-14-1
100.	N,N-dimethylformamide(DMFA)	68-12-2
101.	Dibutyltin dichloride (DBT)	683-18-1



Test Report

Report No. TC.26.02.000814-R1

Date of Issue 2026-03-10

Appendix I

No.	Substance Name	CAS No
102.	Acetic acid, lead salt, basic**	51404-69-4
103.	Basic lead carbonate (trilead bis(carbonate)dihydroxide)**	1319-46-6
104.	Lead oxide sulfate (basic lead sulfate)**	12036-76-9
105.	[Phthalato(2-)]dioxotrilead (dibasic lead phthalate)**	69011-06-9
106.	Dioxobis(stearato)trilead**	12578-12-0
107.	Fatty acids, C16-18, lead salts**	91031-62-8
108.	Lead bis(tetrafluoroborate)**	13814-96-5
109.	Lead cyanamate**	20837-86-9
110.	Lead dinitrate**	10099-74-8
111.	Lead oxide (lead monoxide)**	1317-36-8
112.	Lead tetroxide (orange lead)**	1314-41-6
113.	Lead titanium trioxide**	12060-00-3
114.	Lead Titanium Zirconium Oxide**	12626-81-2
115.	Pentalead tetraoxide sulphate**	12065-90-6
116.	Pyrochlore,antimony lead yellow**	8012-00-8
117.	Silicic acid, barium salt, lead-doped**	68784-75-8
118.	Silicic acid, lead salt**	11120-22-2
119.	Sulfurous acid, lead salt, dibasic**	62229-08-7
120.	Tetraethyllead**	78-00-2
121.	Tetralead trioxide sulphate**	12202-17-4
122.	Trilead dioxide phosphonate**	12141-20-7
123.	Furan	110-00-9
124.	Propylene oxide; 1,2-epoxypropane; methyloxirane	75-56-9
125.	Diethyl sulphate	64-67-5
126.	Dimethyl sulphate	77-78-1
127.	3-ethyl-2-methyl-2-(3-methylbutyl)-1,3-oxazolidine	143860-04-2
128.	Dinoseb	88-85-7
129.	4,4'-methylenedi-o-toluidine	838-88-0
130.	4,4'-oxydianiline and its salts	101-80-4
131.	4-Aminoazobenzene	60-09-3
132.	4-methyl-m-phenylenediamine	95-80-7
133.	6-methoxy-m-toluidine	120-71-8
134.	Biphenyl-4-ylamine	92-67-1
135.	o-aminoazotoluene	97-56-3
136.	o-Toluidine	95-53-4
137.	N-methylacetamide	79-16-3
138.	1-bromopropane; n-propyl bromide	106-94-5
139.	Cadmium**	7440-43-9
140.	Cadmium oxide**	1306-19-0
141.	Dipentyl phthalate (DPP)	131-18-0
142.	4-Nonylphenol, branched and linear, ethoxylated (NPEO)	--
143.	Ammonium pentadecafluorooctanoate (APFO)	3825-26-1
144.	Pentadecafluorooctanoic acid (PFOA)	335-67-1
145.	Cadmium sulphide**	1306-23-6

Test Report

Report No. TC.26.02.000814-R₁

Date of Issue 2026-03-10

Appendix I

No.	Substance Name	CAS No
146.	Disodium 3,3'-[[1,1'-biphenyl]-4,4'-diylbis(azo)]bis(4-aminonaphthalene-1-sulphonate)(C.I. Direct Red 28)	573-58-0
147.	Disodium 4-amino-3-[[4'-[(2,4-diaminophenyl)azo][1,1'-biphenyl]-4-yl]azo] -5-hydroxy-6-(phenylazo)naphthalene-2,7-disulphonate (C.I. Direct Black 38)	1937-37-7
148.	Diethyl phthalate	84-75-3
149.	Imidazolidine-2-thione (2-imidazoline-2-thiol)	96-45-7
150.	Lead di(acetate)**	301-04-2
151.	Trixylenyl phosphate	25155-23-1
152.	1,2-Benzenedicarboxylic acid, diethyl ester, branched and linear	68515-50-4
153.	Cadmium chloride**	10108-64-2
154.	Sodium perborate; perboric acid, sodium salt**	--
155.	Sodium peroxometaborate**	7632-04-4
156.	Cadmium fluoride**	7790-79-6
157.	Cadmium sulphate**	10124-36-4/ 31119-53-6
158.	2-benzotriazol-2-yl-4,6-di-tert-butylphenol (UV-320)	3846-71-7
159.	2-(2H-benzotriazol-2-yl)-4,6-ditertpentylphenol (UV-328)	25973-55-1
160.	2-ethylhexyl 10-ethyl-4,4-dioctyl-7-oxo-8-oxa-3,5-dithia-4-stannatetradecanoate (DOTE)	15571-58-1
161.	reaction mass of 2-ethylhexyl 10-ethyl-4,4-dioctyl-7-oxo-8-oxa-3,5-dithia-4-stannatetradecanoate and 2-ethylhexyl 10-ethyl-4-[[2-[(2-ethylhexyl)oxy]-2-oxoethyl]thio]-4-octyl-7-oxo-8-oxa-3,5-dithia-4-stannatetradecanoate (reaction mass of DOTE and MOTE)	-
162.	1,2-benzenedicarboxylic acid, di-C6-10-alkyl esters; 1,2-benzenedicarboxylic acid, mixed decyl and hexyl and octyl diesters with ≥ 0.3% of diethyl phthalate	68515-51-5 68648-93-1
163.	5-sec-butyl-2-(2,4-dimethylcyclohex-3-en-1-yl)-5-methyl-1,3-dioxane [1], 5-sec-butyl-2-(4,6-dimethylcyclohex-3-en-1-yl)-5-methyl-1,3-dioxane [2] [covering any of the individual stereoisomers of [1] and [2] or any combination thereof]	-
164.	1,3-propanesultone	1120-71-4
165.	2,4-di-tert-butyl-6-(5-chlorobenzotriazol-2-yl)phenol (UV-327)	3864-99-1
166.	2-(2H-benzotriazol-2-yl)-4-(tert-butyl)-6-(sec-butyl)phenol (UV-350)	36437-37-3
167.	Nitrobenzene	98-95-3
168.	Perfluorononan-1-oic acid (2,2,3,3,4,4,5,5,6,6,7,7,8,8,9,9,9-heptadecafluorononanoic acid) and its sodium and ammonium salts	375-95-1 21049-39-8 4149-60-4
169.	Benzo[def]chrysene (Benzo[a]pyrene)	50-32-8
170.	4,4'-isopropylidenediphenol	80-05-7
171.	Nonadecafluorodecanoic acid (PFDA) and its sodium and ammonium salts	335-76-2, 3830-45-3, 3108-42-7
172.	4-Heptylphenol, branched and linear	--
173.	p-(1,1-dimethylpropyl)phenol	80-46-6
174.	Perfluorohexane-1-sulphonic acid and its salts(PFHxS)	355-46-4



Test Report

Report No. TC.26.02.000814-R₁

Date of Issue 2026-03-10

Appendix I

No.	Substance Name	CAS No
175.	1,6,7,8,9,14,15,16,17,17,18,18-Dodecachloropentacyclo [12.2.1.16,9.02,13.05,10]octadeca-7,15-diene ("Dechlorane Plus"™) [covering any of its individual anti- and syn-isomers or any combination thereof]	--
176.	Benz[a]anthracene	56-55-3
177.	Cadmium nitrate**	10325-94-7
178.	Cadmium carbonate**	513-78-0
179.	Cadmium hydroxide**	21041-95-2
180.	Chrysene	218-01-9
181.	Reaction products of 1,3,4-thiadiazolidine-2,5-dithione, formaldehyde and 4-heptylphenol, branched and linear (RP-HP) [with ≥0.1% w/w 4-heptylphenol, branched and linear]	--
182.	Octamethylcyclotetrasiloxane (D4)	556-67-2
183.	Decamethylcyclopentasiloxane (D5)	541-02-6
184.	Dodecamethylcyclohexasiloxane (D6)	540-97-6
185.	Lead	7439-92-1
186.	Disodium octaborate**	12008-41-2
187.	Benzo[ghi]perylene	191-24-2
188.	Terphenyl hydrogenated	61788-32-7
189.	Ethylenediamine (EDA)	107-15-3
190.	Benzene-1,2,4-tricarboxylic acid 1,2-anhydride (trimellitic anhydride) (TMA)	552-30-7
191.	Dicyclohexyl phthalate (DCHP)	84-61-7
192.	2,2-bis(4'-hydroxyphenyl)-4-methylpentane	6807-17-6
193.	Benzo[k]fluoranthene	207-08-9
194.	Fluoranthene	206-44-0
195.	Phenanthrene	85-01-8
196.	Pyrene	129-00-0
197.	1,7,7-trimethyl-3-(phenylmethylene)bicyclo[2.2.1]heptan-2-one (3-benzylidene camphor)	15087-24-8
198.	2,3,3,3-tetrafluoro-2-(heptafluoropropoxy)propionic acid, its salts and its acyl halides (covering any of their individual isomers and combinations thereof)	-
199.	2-methoxyethyl acetate	110-49-6
200.	Tris(4-nonylphenyl, branched and linear) phosphite (TNPP)	-
201.	4-tert-butylphenol (PTBP)	98-54-4
202.	2-benzyl-2-dimethylamino-4'-morpholinobutyrophenone	119313-12-1
203.	2-methyl-1-(4-methylthiophenyl)-2-morpholinopropan-1-one	71868-10-5
204.	Diisohexyl phthalate	71850-09-4
205.	Perfluorobutane sulfonic acid (PFBS) and its salts	-
206.	1-vinylimidazole	1072-63-5
207.	2-methylimidazole	693-98-1
208.	Dibutylbis(pentane-2,4-dionato-O,O')tin	22673-19-4
209.	Butyl 4-hydroxybenzoate (Butylparaben)	94-26-8
210.	Bis(2-(2-methoxyethoxy)ethyl)ether	143-24-8



Test Report

Report No. TC.26.02.000814-R₁

Date of Issue 2026-03-10

Appendix I

No.	Substance Name	CAS No
211.	Diocetyl tin dilaurate, stannane, dioctyl-, bis(coco acyloxy) derivs., and any other stannane, dioctyl-, bis(fatty acyloxy) derivs. wherein C12 is the predominant carbon number of the fatty acyloxy moiety	-
212.	1,4-dioxane	123-91-1
213.	2,2-bis(bromomethyl)propane-1,3-diol (BMP) 2,2-dimethylpropan-1-ol, tribromo derivative / 3-bromo-2,2-bis(bromomethyl)-1-propanol (TBNPA) 2,3-dibromo-1-propanol (2,3-DBPA)	3296-90-0, 36483-57-5/ 1522-92-5, 96-13-9
214.	2-(4-tert-butylbenzyl)propionaldehyde and its individual stereoisomers	-
215.	4,4'-(1-methylpropylidene)bisphenol(bisphenol B)	77-40-7
216.	glutaral	111-30-8
217.	Medium-chain chlorinated paraffins (MCCP) [UVCB substances consisting of more than or equal to 80% linear chloroalkanes with carbon chain lengths within the range from C14 to C17]	-
218.	Orthoboric acid, sodium salt**	13840-56-7
219.	Phenol, alkylation products (mainly in para position) with C12-rich branched alkyl chains from oligomerisation, covering any individual isomers and/ or combinations thereof (PDDP)	-
220.	6,6'-di-tert-butyl-2,2'-methylenedi-p-cresol (DBMC)	119-47-1
221.	Tris(2-methoxyethoxy)vinylsilane	1067-53-4
222.	(±)-1,7,7-trimethyl-3-[(4-methylphenyl)methylene]bicyclo[2.2.1]heptan-2-one covering any of the individual isomers and/or combinations thereof (4-MBC)	-
223.	S-(tricyclo[5.2.1.0 ^{2,6}]deca-3-en-8(or 9)-yl O-(isopropyl or isobutyl or 2-ethylhexyl) O-(isopropyl or isobutyl or 2-ethylhexyl) phosphorodithioate	255881-94-8
224.	N-(hydroxymethyl)acrylamide	924-42-5
225.	1,1'-[ethane-1,2-diylbis(oxy)]bis[2,4,6-tribromobenzene] (BTBPE)	37853-59-1
226.	2,2',6,6'-tetrabromo-4,4'-isopropylidenediphenol (TBBPA)	79-94-7
227.	4,4'-sulphonyldiphenol (BPS)	80-09-1
228.	Barium diboron tetraoxide**	13701-59-2
229.	bis(2-ethylhexyl) tetrabromophthalate covering any of the individual isomers and/or combinations thereof (TBPH)	-
230.	Isobutyl 4-hydroxybenzoate	4247-02-3
231.	Melamine	108-78-1
232.	Perfluoroheptanoic acid(PFHpA) and its salts	-
233.	reaction mass of 2,2,3,3,5,5,6,6-octafluoro-4-(1,1,1,2,3,3,3-heptafluoropropan-2-yl)morpholine and 2,2,3,3,5,5,6,6-octafluoro-4-(heptafluoropropyl)morpholine	-
234.	Diphenyl(2,4,6-trimethylbenzoyl)phosphine oxide	75980-60-8
235.	bis(4-chlorophenyl) sulphone	80-07-9
236.	2,4,6-tri-tert-butylphenol (2,4,6-TTBP)	732-26-3
237.	2-(2H-benzotriazol-2-yl)-4-(1,1,3,3-tetramethylbutyl)phenol	3147-75-9
238.	2-(dimethylamino)-2-[(4-methylphenyl)methyl]-1-[4-(morpholin-4-yl)phenyl]butan-1-one	119344-86-4
239.	Bumetrizole (UV-326)	3896-11-5
240.	Oligomerisation and alkylation reaction products of 2-phenylpropene and phenol (OAPP)	-
241.	Bis(α,α-dimethylbenzyl) peroxide	80-43-3



Test Report

Report No. TC.26.02.000814-R₁

Date of Issue 2026-03-10

Appendix I

No.	Substance Name	CAS No
242.	Triphenyl phosphate (TPhP)	115-86-6
243.	6-[(C10-C13)-alkyl-(branched, unsaturated)-2,5-dioxopyrrolidin-1-yl]hexanoic acid	2156592-54-8
244.	O,O,O-triphenyl phosphorothioate (TPPT)	597-82-0
245.	Octamethyltrisiloxane	107-51-7
246.	Perfluamine	338-83-0
247.	Reaction mass of: triphenylthiophosphate and tertiary butylated phenyl derivatives	192268-65-8
248.	1,1,1,3,5,5,5-heptamethyl-3-[(trimethylsilyl)oxy]trisiloxane (M3T)	17928-28-8
249.	Decamethyltetrasiloxane (L4)	141-62-8
250.	Tetra(sodium/potassium) 7-[(E)-{2-acetamido-4-[(E)-(4-{[4-chloro-6-({2-[(4-fluoro-6-{[4-(vinylsulfonyl)phenyl]amino}-1,3,5-triazine-2-yl)amino]propyl}amino)-1,3,5-triazine-2-yl]amino}-5-sulfonato-1-naphthyl)diazenyl]-5-methoxyphenyl}diazenyl]-1,3,6-naphthalenetrisulfonate (Reactive Brown 51)	-
251.	1,1'-(ethane-1,2-diyl)bis[pentabromobenzene] (DBDPE)	84852-53-9
252.	n-hexane	110-54-3
253.	4,4'-[2,2,2-trifluoro-1-(trifluoromethyl)ethylidene]diphenol and its salts	-

-End of Report-